



SM-2209

AWS A5.9 ER2209
JIS Z3321 YS2209
EN ISO 14343-A - G 22 9 3 N L

HYUNDAI WELDING CO., LTD.



❖ Specification

<i>AWS A5.9</i>	ER2209
<i>JIS Z3321</i>	YS2209
<i>EN ISO 14343</i>	G 22 9 3 N L

❖ Applications

Welding of UNS S31803, S32205
(Independent water power plant)

❖ Characteristics on Usage

1. Weld metal has 30~60% ferrite contents
2. Due to the high chromium contents, corrosion resistance is excellent in most environments(chloride environment)
3. Superior pitting resistance(PREN ≥ 34)

❖ Shielding gas

100% Ar, Ar+2% O₂

❖ Polarity

GMAW : DC+

❖ Packing


SM-2209	MIG	Size(mm)	1.0	1.2
		Weight	12.5 kg	



1. Mechanical Properties & Chemical Composition of All-Weld Metal (GMAW)

❖ Welding Conditions

Method by AWS Spec.

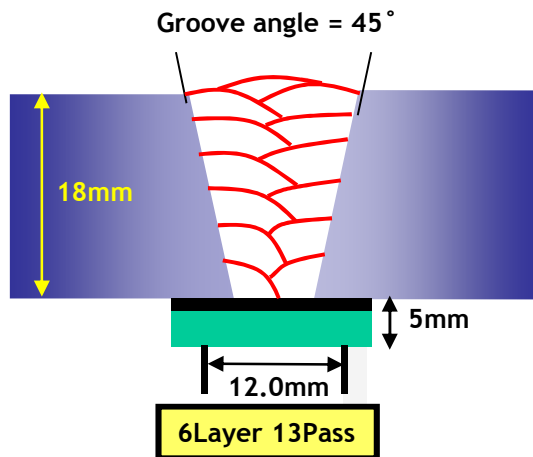

- Size(mm) : 1.2mm
- Shielding gas : Ar+2% O₂
- Flow(ℓ /min.) : 15~20
- Ampere/Voltage : 190~200A/26~27V
- Speed(cm/min.) : 30
- Heat input(KJ/cm) : 10~15.0
- Base metal: UNS S31803

1-2 Chemical composition of the wire (wt%)

C	Si	Mn	P	S	Ni	Cr	Mo	Cu	N
0.018	0.47	1.68	0.014	0.001	8.75	22.90	3.20	0.09	0.16
≤0.03	≤0.9	0.5~2.0	≤0.03	≤0.03	7.5~9.5	21.5~23.5	2.5~3.5	≤0.75	0.08~0.2
AWS A5.9 ER2209									

1-3 Chemical composition of All weld metal (wt%)

C	Si	Mn	P	S	Ni	Cr	Mo	Cu	N ₂	PREN
0.020	0.42	1.73	0.015	0.002	8.93	22.51	3.15	0.139	0.16	34.52

* PREN = Cr + 3.3×Mo + 16×N

1-4 Radiographic Test

Consumable	Specification	Accepted	Rejected
SM-2209	AWS A5.4	○	

This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



1. Mechanical Properties & Chemical Composition of All Weld Metal (GMAW)

1-5 Mechanical properties of All-weld metal

Tensile Test Results.		
TS (MPa)	EI (%)	
784.0	30.6	
AWS A5.4 E2209	≥ 690	≥ 20

CVN Impact (Joule)					
°C	X1	X2	X3	Avg.	
-20	86	92	73	83.6	

1-6 Ferrite content of weld metal

Consumable	Shaeffler	WRC(1992)	FERRITSCOPE (MP-30)
SM-2209	46.4	40.8	34

1-7 Ferric Chloride Pitting Test (ASTM G48 Method A)

Consumable	Specimen Weight(g)		Weight loss(g)	Remark (Pitting)
	Before	After		
SM-2209 (1G)	116.0912	116.0906	0.0006	No Pitting

* Temperature : 25°C ± , Period : 24Hr

This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.