

# **SM-316L**



## ❖ Specification

<i>AWS A5.9</i>	ER316L
<i>JIS Z3321</i>	YS316L

## ❖ Applications

MIG welding of low carbon 18% Cr- 12% Ni - 2% Mo steel for Chemical industries and nuclear reactors.

## ❖ Characteristics on Usage

SM-316L is an austenitic type stainless steel wire , the weld metal contains ferrite and crack sensitivity is extremely good. The Usability, such as arc stability and assimilability of welds to base metal is extremely excellent.

Resistance to corrosion and mechanical properties of weld metal are great.

## ❖ Note on Usage

Use 100% Ar gas or Ar+2~5% O<sub>2</sub> gas

## ❖ Packing


Dia.(mm)	0.8	0.9	1.0	1.2
Spool (kg) *including ball pac	12.5		15	



## Mechanical Properties & Chemical Composition of All Weld Metal

### ❖ Welding Conditions

Method by AWS Spec.

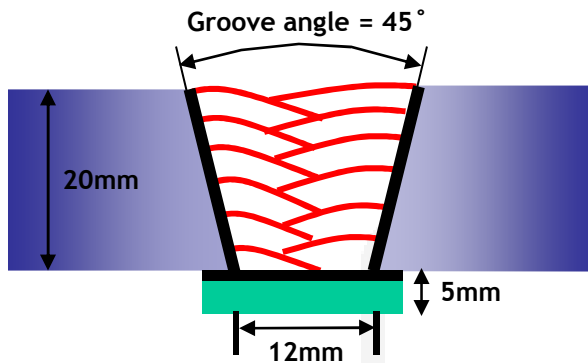

[ Joint Preparation & Layer Details ]

<b>Diameter(mm)</b>	: 1.2mm
<b>Shielding Gas</b>	: Ar+2% O <sub>2</sub>
<b>Flow Rate(ℓ /min.)</b>	: 15~20
<b>Amp./ Volt.</b>	: 230/27
<b>Stick-Out(mm)</b>	: 20
<b>Pre-Heat(°C)</b>	: R.T .
<b>Interpass Temp.(°C)</b>	: 150±15
<b>Polarity</b>	: DC(+)

### ❖ Mechanical Properties of All weld metal

Consumable	Tensile Test		CVN Impact test (Joule)	
	TS(MPa)	EI(%)	0°C	-196°C
SM-316L	546	38.2	84.6	33.6

### ❖ Chemical Analysis of the wire(wt%)

Consumable	Shielding Gas	Chemical Composition (%)								
		C	Si	Mn	P	S	Ni	Cr	Mo	Cu
SM-316L	Ar+2% O <sub>2</sub>	0.017	0.46	1.75	0.021	0.010	11.5	18.5	2.17	0.12
AWS A5.9 ER316L		≤0.03	0.30~ 0.65	1.0~ 2.5	≤0.03	≤0.03	11.0~ 14.0	18.0~ 20.0	2.0~ 3.0	≤0.75


This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



**Mechanical Properties  
& Chemical Composition of All Weld Metal**

❖ **δ – Ferrite No.**

Consumable	Shielding Gas	Diagram			FERITSCOPE MP-30 * (FISCHER)
		Schaeffler	DeLong	WRC(1992)	
SM-316L	Ar+2% O2	8.5	12.7	10.9	14.0



This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.