

# **ST-2209**

**AWS A5.9 ER2209**  
**JIS Z3321 YS2209**  
**EN ISO 14343-A - W 22 9 3 N L**

---

**HYUNDAI WELDING CO., LTD.**



## ❖ Specification

<i>AWS A5.9</i>	ER2209
<i>JIS Z3321</i>	YS2209
<i>EN ISO 14343</i>	W 22 9 3 N L

## ❖ Applications

Welding of UNS S31803, S32205  
(Independent water power plant)

## ❖ Characteristics on Usage

1. Weld metal has 30~60% ferrite contents
2. Due to the high chromium contents, corrosion resistance is excellent in most environments(chloride environment)
3. Superior pitting resistance(PREN  $\geq 34$ )

## ❖ Shielding gas

100% Ar

## ❖ Polarity

GTAW : DC-

## ❖ Packing


ST-2209	TIG	Size(mm)	2.4mm X 1000mm
		Weight	5 kg



# 1. Mechanical Properties & Chemical Composition of All-Weld Metal (GTAW)

## ❖ Welding Conditions

Method by AWS Spec.

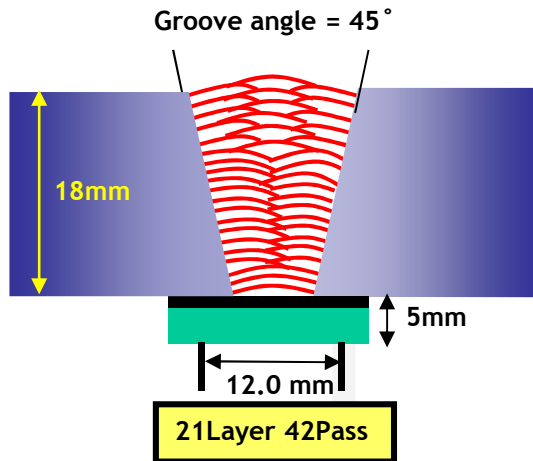

Size(mm)	: 2.4mm
Shielding gas	: 100% Ar
Flow(ℓ /min.)	: 15~20
Ampere/Voltage	: 150~160A/13~14V
Speed(cm/min.)	: 12.4~14.1
Heat input(KJ/cm)	: 5.0~15.0
Base metal:	UNS S31803

### 1-2 Chemical composition of the wire (wt%)

C	Si	Mn	P	S	Ni	Cr	Mo	Cu	N
0.018	0.47	1.68	0.014	0.001	8.75	22.90	3.20	0.09	0.16
≤0.03	≤0.9	0.5~2.0	≤0.03	≤0.03	7.5~9.5	21.5~23.5	2.5~3.5	≤0.75	0.08~0.2
AWS A5.9 ER2209									

### 1-3 Chemical composition of All weld metal (wt%)

C	Si	Mn	P	S	Ni	Cr	Mo	Cu	N2	PREN
0.020	0.38	1.68	0.020	0.005	8.31	22.7	3.01	0.03	0.11	34.39

\* PREN = Cr + 3.3×Mo + 16×N

### 1-4 Radiographic Test

Consumable	Specification	Accepted	Rejected
ST-2209	AWS A5.4	○	

This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.





# 1. Mechanical Properties & Chemical Composition of All Weld Metal (GTAW)

## 1-5 Mechanical properties of All-weld metal

Tensile Test Results.		
TS (MPa)		EI (%)
813		27
AWS A5.4 E2209	≥ 690	≥ 20

CVN Impact (Joule)				
°C	X1	X2	X3	Avg.
-20	192	166	222	195
-50	182	188	172	180

## 1-6 Vickers hardness test(H<sub>v</sub> :10kg )

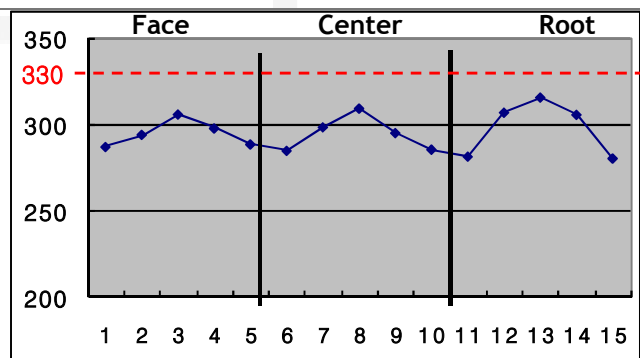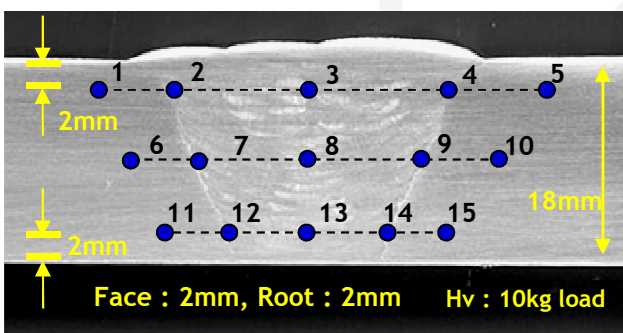

H <sub>v</sub> 10, Vickers hardness test							
1	2	3	4	5	6	7	8
286.9	294.0	305.9	297.8	288.5	284.7	298.46	309.32
9	10	11	12	13	14	15	
295.06	285.4	281.3	307.0	315.8	305.7	280.3	


This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.




# 1. Mechanical Properties & Chemical Composition of All Weld Metal (GTAW)

## 1-7 Ferrite content of weld metal


Consumable	Shaeffler	WRC(1992)	ASTM E562
ST-2209	55.1	66.7	40.1

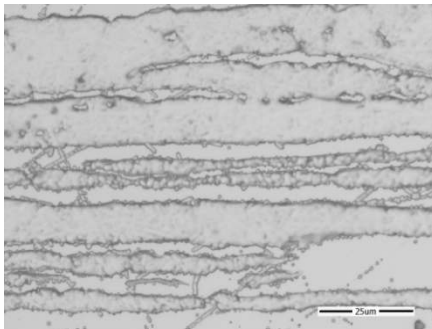

**Base Metal**

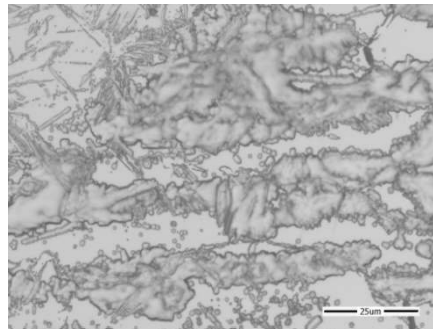


**HAZ**

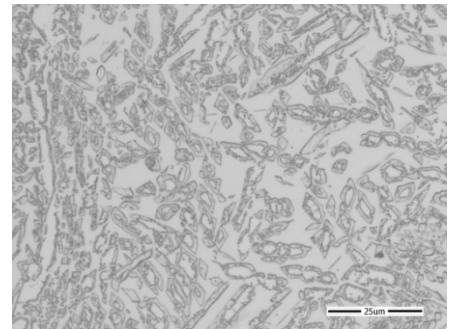

**Weld Metal**

## 1-8 Mechanical properties of weld metal(Butt welding)

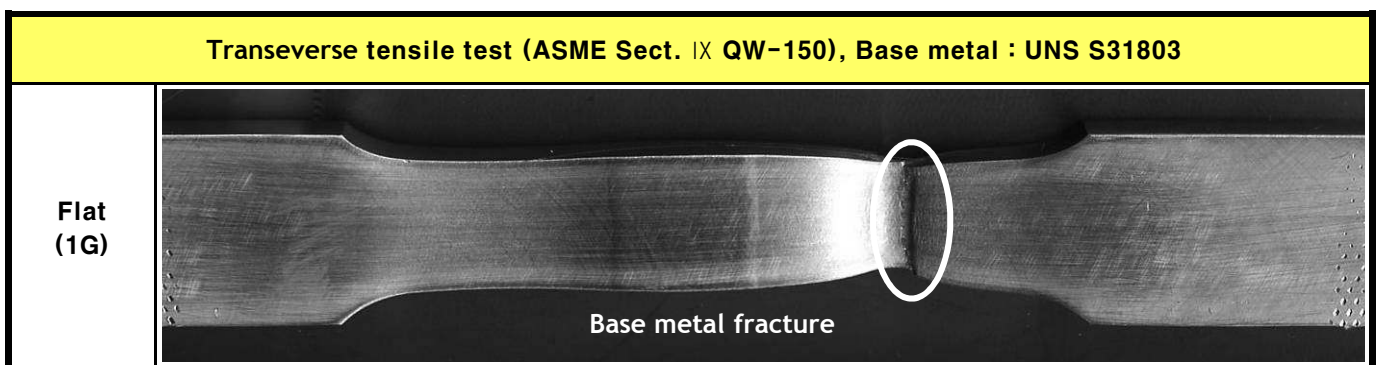


This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



# 1. Mechanical Properties of Butt Weld Metal (GTAW)

## 1-9 Bending test

### ● Transverse Bending Test (Face, Root, Side)

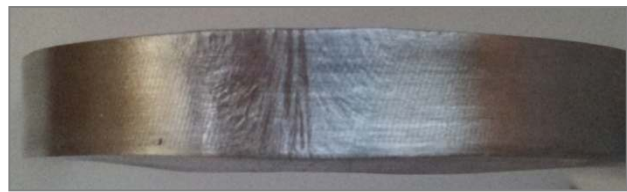

Face (Non-Crack )

Root (Non-Crack )

Side (Non-Crack)

## 1-10 Ferric Chloride Pitting Test (ASTM G48 Method A)

Consumable	Specimen Weight(g)		Weight loss(g)	Remark (Pitting)
	Before	After		
ST-2209 (1G)	116.0912	116.0906	0.0006	No Pitting

\* Temperature : 25°C± , Period : 24Hr



Before

After

This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.